

Measurement of Thermomagnetic Convection Effect in a Cooling Process

Sleimane Nasser El Dine, Xavier Mininger, Caroline Nore, Sophie Neveu,

Frédéric Bouillault

► To cite this version:

Sleimane Nasser El Dine, Xavier Mininger, Caroline Nore, Sophie Neveu, Frédéric Bouillault. Measurement of Thermomagnetic Convection Effect in a Cooling Process. International Conference on Magnetic Fluids ICMF 2019, Jul 2019, Paris, France. hal-03144416

HAL Id: hal-03144416 https://centralesupelec.hal.science/hal-03144416v1

Submitted on 18 Feb 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Limsi

Measurement of Thermomagnetic Convection Effect in a Cooling Process

S. Nasser El Dine^{1,2}, X. Mininger¹, C. Nore², S. Neveu³, F. Bouillault¹



¹GeePs, UMR 8507 CNRS / CentraleSupelec - Sorbonne Université et UPSud, 91192 Gif sur Yvette cedex, France, Sleimane.Nassereldine@geeps.centralesupelec.fr, Xavier.Mininger@geeps.centralesupelec.fr, Frederic.Bouillault@geeps.centralesupelec.fr ²LIMSI, CNRS, Univ. Paris-Sud, Université Paris-Saclay, F-91405 Orsay, France, Caroline.Nore@limsi.fr

³PHENIX, UMR 8234, Sorbonne Université, 75252 PARIS Cedex 05, France, sophie.neveu@upmc.fr

Context & Motivation

Cooling of electromagnetic systems (e.g. transformers) ferrofluids, using i.e. suspensions of magnetic nanoparticles in a liquid carrier, is studied at GeePs and LIMSI labs.




Thermomagnetic Convection Effect

Results

Two sensors record temperature in the fluid and at the coil.


The current direction in each resistor is initially the same, then it every 60 minutes to activate/deactivate the reverses in thermomagnetic experiment convection the the and computation.

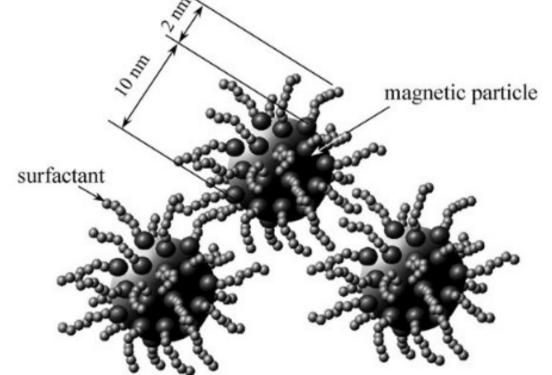


The objective is to understand the effect of the nanoparticles on heat transfers using both experimental and numerical approaches.

Experimental & Numerical Setup


An experimental setup uses a coil immersed in a cylinder filled with a cobalt-based surfactant ferrofluid (5% volume fraction of nanoparticles), carrier liquid is a vegetable oil

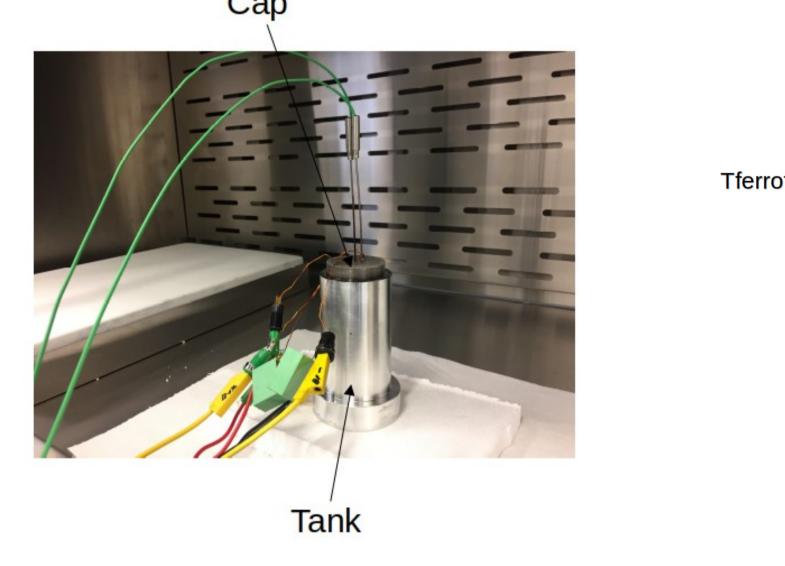

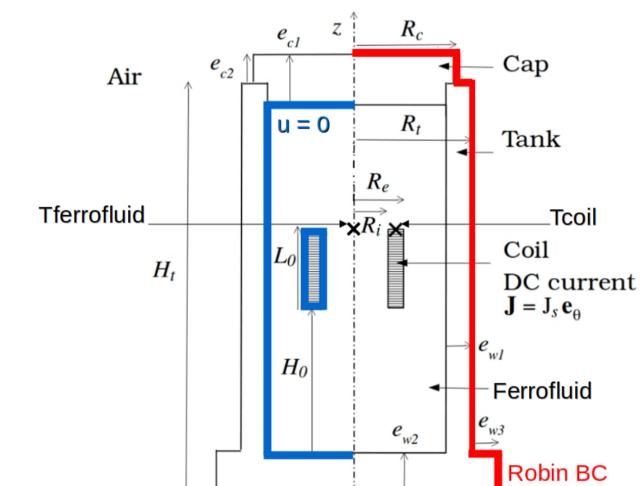

Neumann BC

Setup model

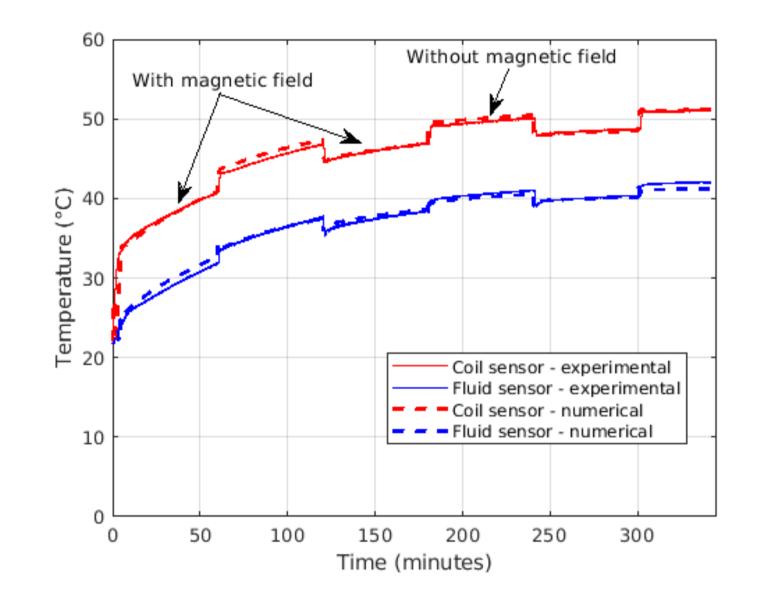


Crenellations with equal 2,2 °C amplitude of are approximately reproduced.


the thermomagnetic When convection is active, the coil temperature decreases.

Impact on velocity and temperature

The fluid flow around the coil is modified by the Helmholtz magnetic force. The temperature decrease is 1.9 °C.

Velocity magnitude U (m/s), streamlines (u,w) and temperature (°C) at t = 280 min and t = 330 min respectively:

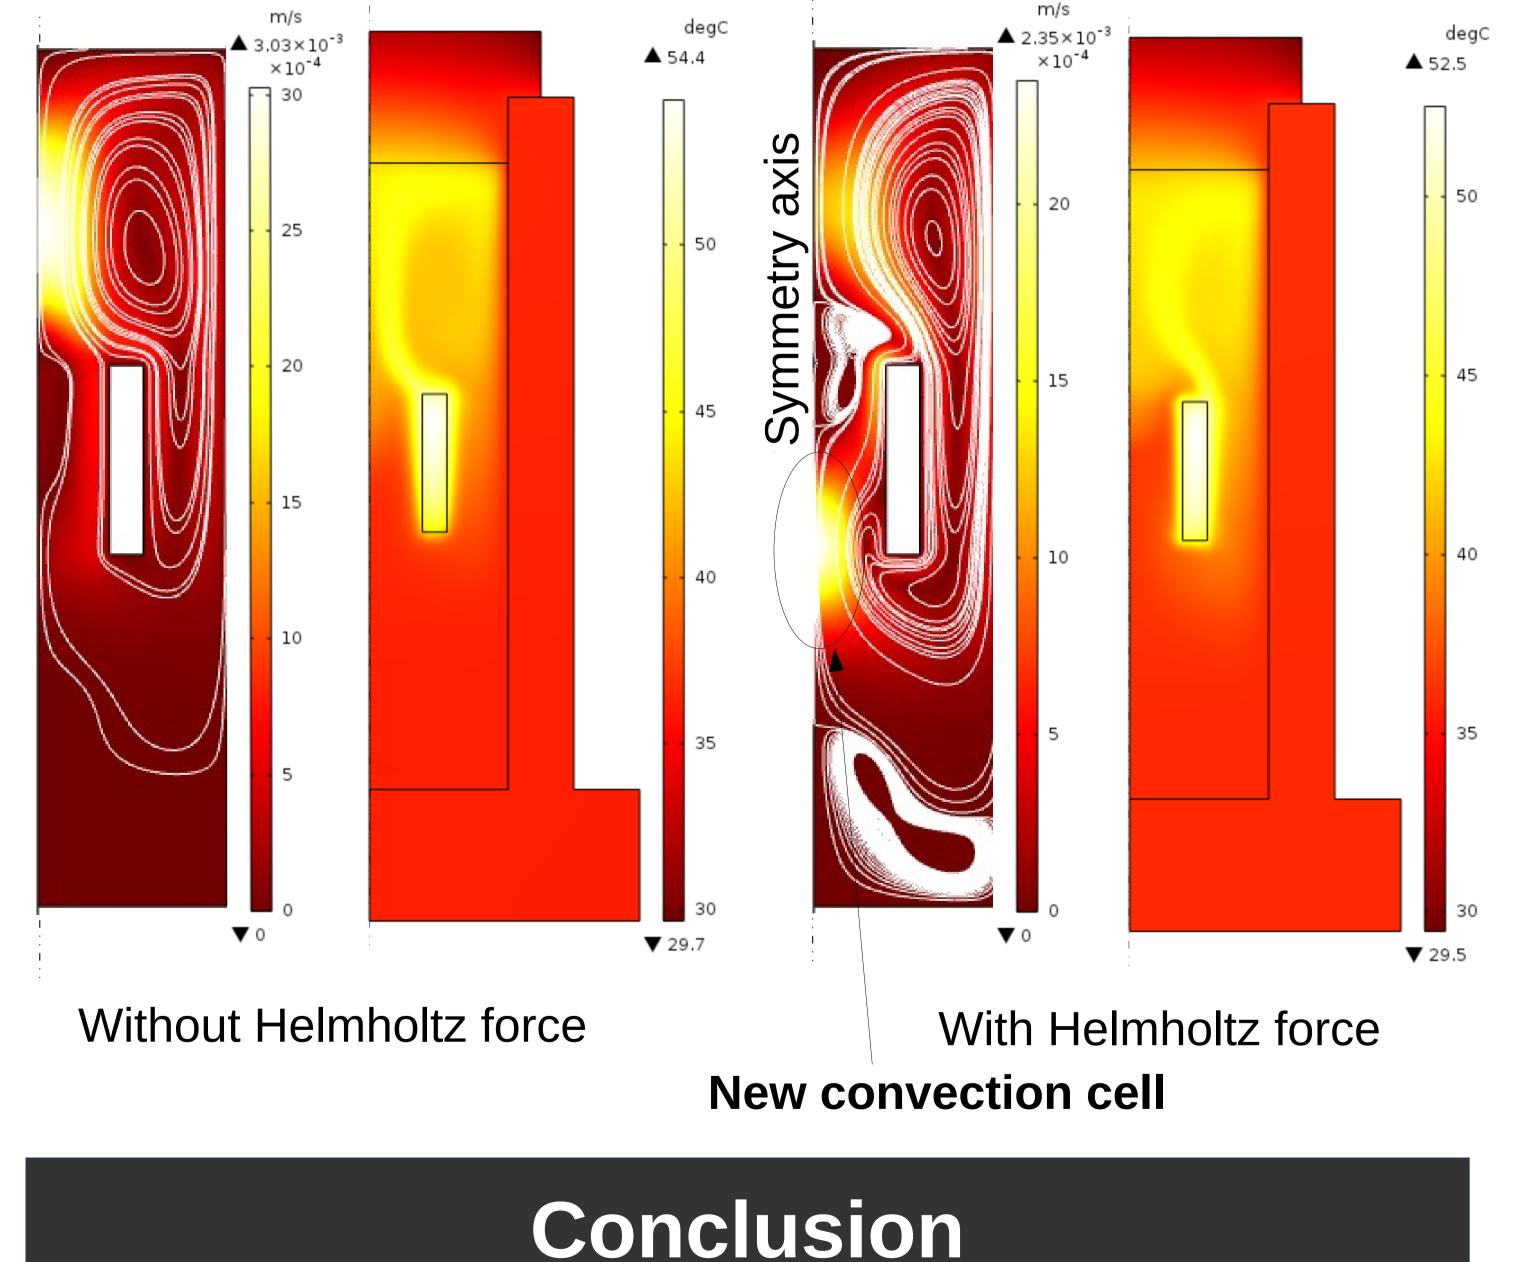

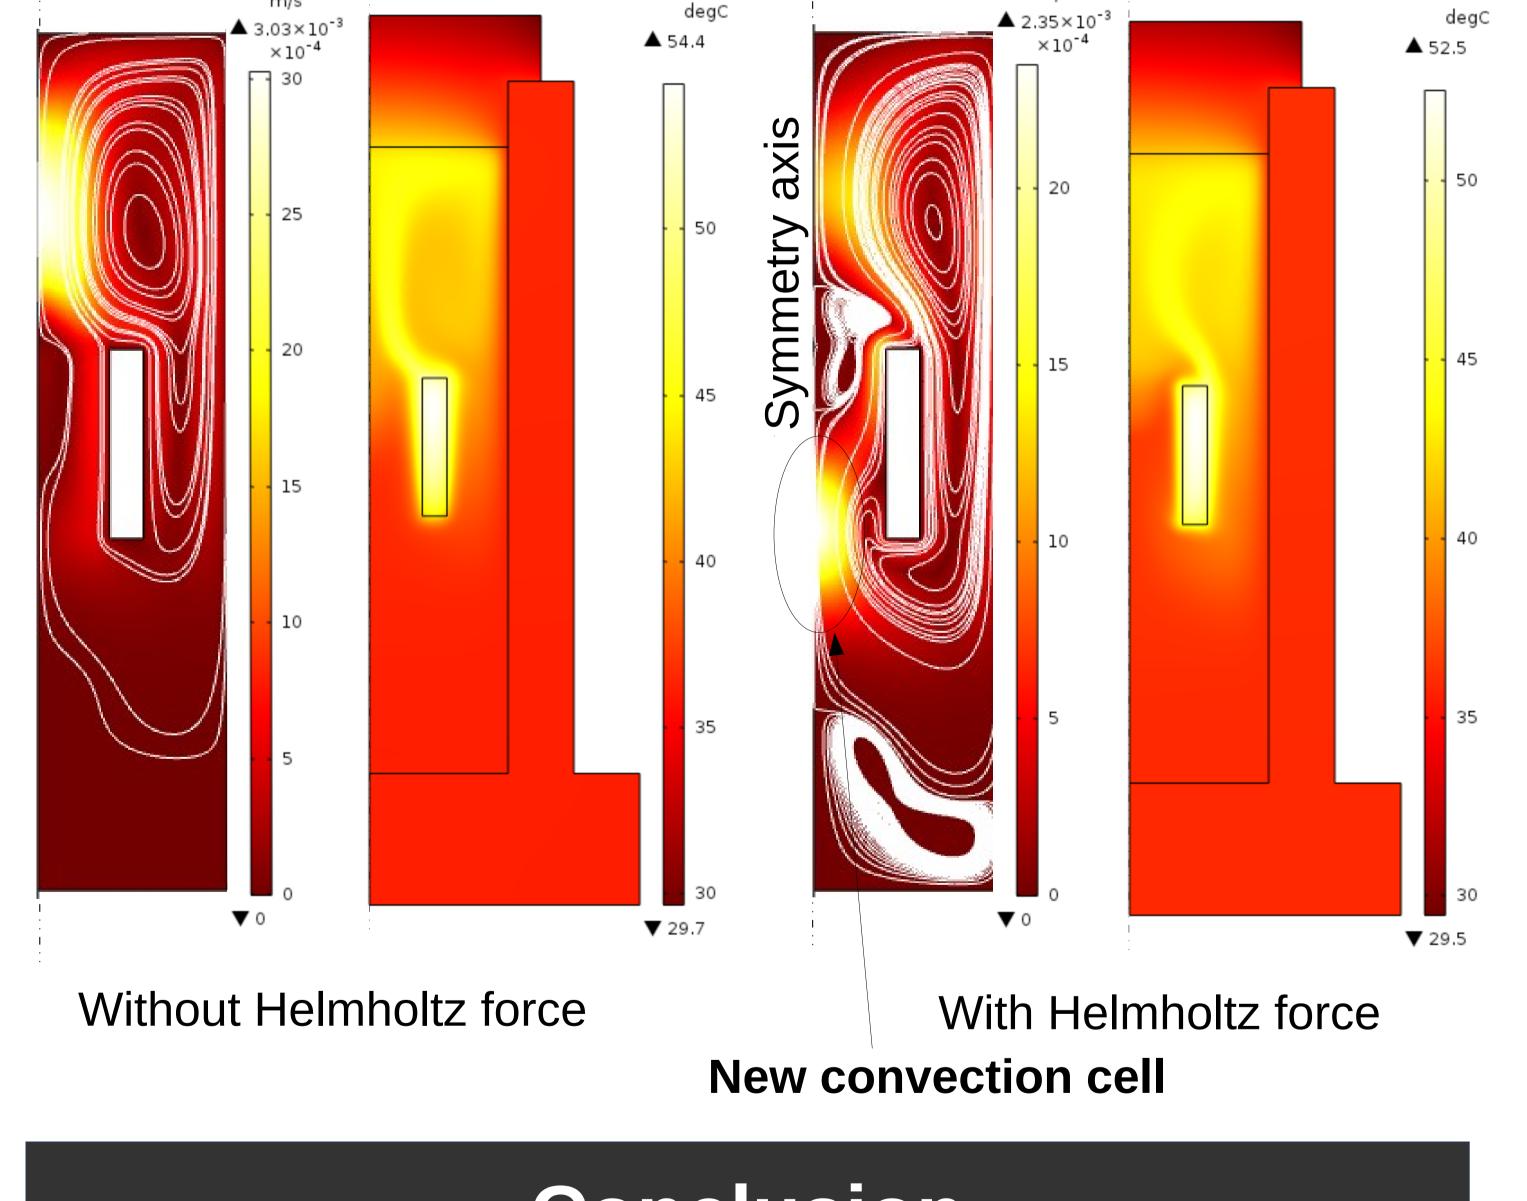

Langevin's theory for linear magnetic material is used for the M-H relation: $M = \chi(T)H \qquad \chi(T) = \frac{\phi \mu_0 \pi d^3 M_{s,p}(T)^2}{18 K_B T}$

Navier-Stokes, energy and magnetostatic equations are solved Boussinesq approximation and an incompressible using Newtonian fluid.

$$\rho_{l} \frac{Du}{Dt} + \nabla p - \eta \Delta u = \rho_{l} \beta g (T - T_{0}) e_{z} - \mu_{0} \frac{H^{2}}{2} \nabla \chi(T) \quad \text{in } \Omega_{f}$$

$$\nabla \cdot u = 0$$

$$u = 0$$

$$u = 0$$
Buoyancy force
$$\int_{in \Omega_{f}} \frac{\partial \Omega_{f}}{\partial t} = \int_{in \Omega_{f}} \frac{\nabla \times H}{\partial t} = J \quad \text{in } \Omega$$

$$\nabla \cdot (\mu H) = 0 \quad \text{in } \Omega$$

$$Helmholtz \text{ force}$$

$$\rho_{l} c_{p} \frac{DT}{Dt} - \nabla \cdot (\lambda \nabla T) = \frac{J^{2}}{\sigma} \qquad \text{in } \Omega$$


$$-(\lambda \nabla T)n = h(T - T_{0})n \quad \text{on } \partial \Omega_{R}$$

$$-(\lambda \nabla T)n = 0 \qquad \text{on } \partial \Omega_{N}$$

$$T_{t=0} = T_{0} \qquad \text{in } \Omega$$
The thermophysical properties of the ferrofluid are calculated using mixed laws.

Activation Method

The solenoid consists of a copper coil, in the form of a two-wire conductor as below:

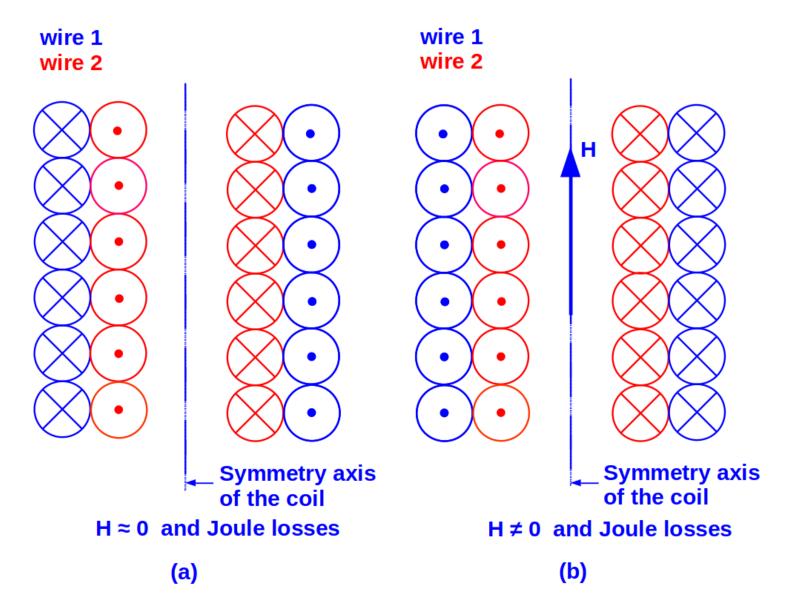

(a) Currents directions in the two wires opposite: are Thermomagnetic convection deactivated

(b) Currents directions in the two identical: wires are Thermomagnetic convection activated

An experimental setup is developed to study the heat transfer of an electromagnetic system cooled by a ferrofluid. The modeling assumptions lead to numerical results in agreement with the measurements. The thermomagnetic convection leads to a decrease of coil temperature. Further developments will turn to more realistic devices with different types of load.

References

R. E. Rosensweig, Ann. Rev. Fluid Mech. 1987. 19 : 437-63 Neuringer & Rosensweig, Physics of Fluids, Vol.7, No.12, Dec 1964 S. Odenbach, PAMM, Proc. Appl. Math. Mech. 1 (2002)